

# SLEIPNER

Cold work tool steel

COLD WORK

PLASTIC MOULDING

HOT WORK

HIGH PERFORMANCE STEEL



This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses.  
It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

## General

Sleipner is a chromium-molybdenum-vanadium alloyed tool steel which is characterised by:

- Good wear resistance
- Good chipping resistance
- High compressive strength
- High hardness (>60 HRC) after high temperature tempering
- Good through-hardening properties
- Good stability in hardening
- Good resistance to tempering back
- Good WEDM properties
- Good machinability and grindability
- Good surface treatment properties.

Typical analysis %	C 0,9	Si 0,9	Mn 0,5	Cr 7,8	Mo 2,5	V 0,5
Standard spec.	None					
Delivery condition	Soft annealed to approx. 235 HB					
Colour code	Blue/brown					

## Properties

### PHYSICAL DATA

Hardened and tempered to 62 HRC. Data at room and elevated temperatures.

Temperature	20°C (68°F)	200°C (390°F)	400°C (750°F)
Density kg/m <sup>3</sup> lbs/in <sup>3</sup>	7 730 0,279	7 680 0,277	7 620 0,275
Modulus of elasticity MPa ksi	205 000 297 000	190 000 276 000	180 000 261 000
Coefficient of thermal expansion –after low tempera- ture tempering (60 HRC) per °C from 20°C per °F from 68°F	– –	12,7 x 10 <sup>-6</sup> 7,1 x 10 <sup>-6</sup>	– –
–after high tempera- ture tempering per °C from 20°C per °F from 68°F	– –	11,6 x 10 <sup>-6</sup> 6,4 x 10 <sup>-6</sup>	12,4 x 10 <sup>-6</sup> 6,9 x 10 <sup>-6</sup>
Thermal conductivity W/m • °C Btu in/(ft <sup>2</sup> h °F)	– –	20 140	25 170
Specific heat J/kg °C Btu/lb. °F	460 0,11	– –	– –

## Applications

Sleipner is a general purpose steel for cold work tooling. It has a mixed-abrasive wear profile and a good resistance to chipping. Furthermore a high hardness (>60 HRC) can be obtained after high temperature tempering. This means that surface treatments such as nitriding or PVD can be made on a high strength substrate. Also, it means that complicated shapes with hardness levels >60 HRC can be wire EDM'd from blocks with relatively thick cross-sections with a much reduced risk of cracking.

Sleipner is recommended for medium run tooling applications where a resistance to mixed or abrasive wear and a good resistance to chipping are required.

#### Examples:

- Blanking and fine blanking
- Shearing
- Forming
- Coining
- Cold forging
- Cold extrusion
- Thread rolling
- Drawing and deep drawing
- Powder pressing

### COMPRESSIVE STRENGTH


The figures should be considered as approximate.

Hardness HRC	Compressive yield strength R <sub>c0,2</sub>	
	MPa	ksi
50	1 700	250
55	2 050	300
60	2 350	340
62	2 500	360
64	2 650	380

### CHIPPING RESISTANCE

Relative chipping resistance for Sverker 21, Sleipner and Rigor at the same hardness level.


Relative chipping resistance

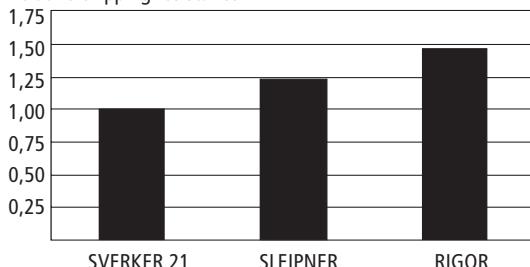

## ABRASIVE WEAR RESISTANCE

Relative abrasive wear resistance for Sverker 21, Sleipner and Rigor at the same hardness level (low value means better wear resistance).

Relative abrasive wear rate

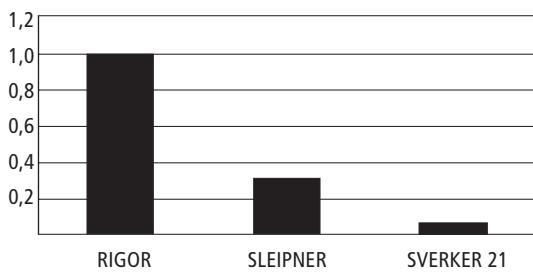

## Heat treatment

### SOFT ANNEALING

Protect the steel and heat through to 850°C (1560°F). Then cool in the furnace at 10°C (20°F) per hour to 650°C (1200°F), then freely in air.

### STRESS RELIEVING

After rough machining the tool should be heated through to 650°C (1200°F) and held for 2 h. Cool slowly to 500°C (930°F) then freely in air.

### HARDENING

*Preheating temperature: 650–750°C (1200–1380°F)*

*Austenitizing temperature: 950–1080°C (1740–1980°F) but usually 1030–1050°C (1890–1920°F)*

*Holding time: 30 min*


*Protect the part against decarburization and oxidation during hardening.*

### QUENCHING MEDIA

- Forced gas/circulating atmosphere
- Vacuum (high speed gas with sufficient overpressure)
- Martempering bath or fluidized bed at 500–550°C (930–1020°F)
- Martempering bath or fluidized bed at approx. 200–350°C (390–660°F)
- Oil (only very simple geometries)


*Note: Temper the tool as soon as its temperature reaches 50–70°C (120–160°F)*

*Hardness, retained austenite and grain size as function of austenitizing temperature*

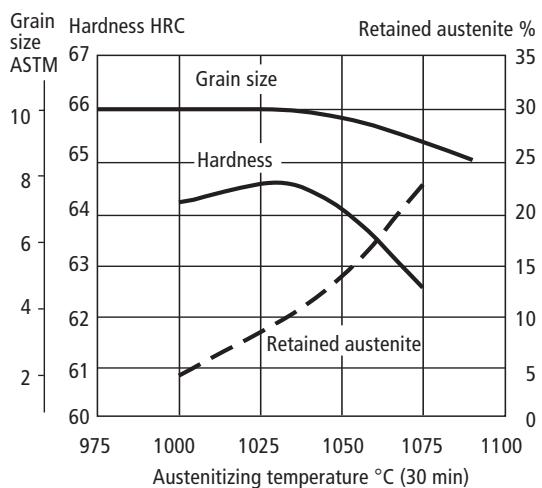


### TEMPERING

Choose the tempering temperature according to the hardness required by reference to the tempering graph. Temper at least twice with intermediate cooling to room temperature. The lowest tempering temperature which should be used is 180°C (360°F). The minimum holding time at temperature is 2 h.

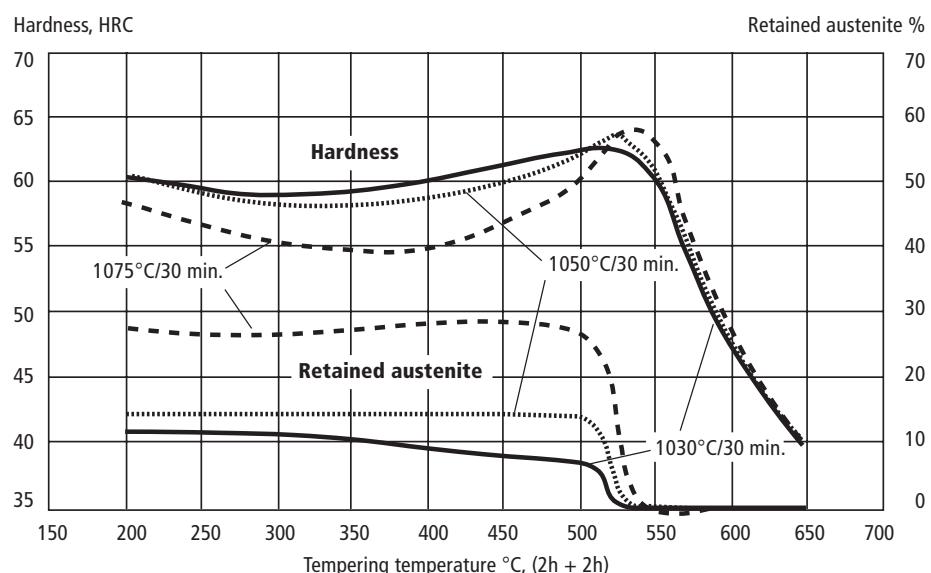

*CCT-graph*

Austenizing temperature 1030°C (1890°F). Holding time 30 min.

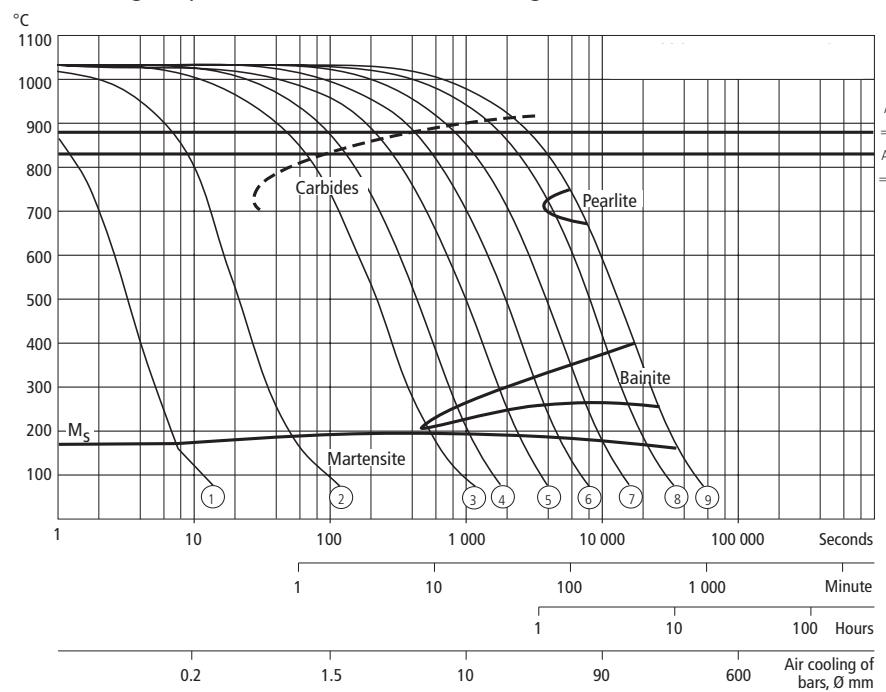


$A_{c1f} = 880^\circ\text{C}$

$A_{c1s} = 830^\circ\text{C}$

Cooling curve no.	Hardness HV 10	$T_{800-500}$ (sec.)
1	824	2
2	824	11
3	813	140
4	813	280
5	813	630
6	813	1241
7	724	2482
8	649	5215
9	572	8360

*TTT-graph*

Austenizing temperature 1030°C (1890°F). Holding time 30 min.

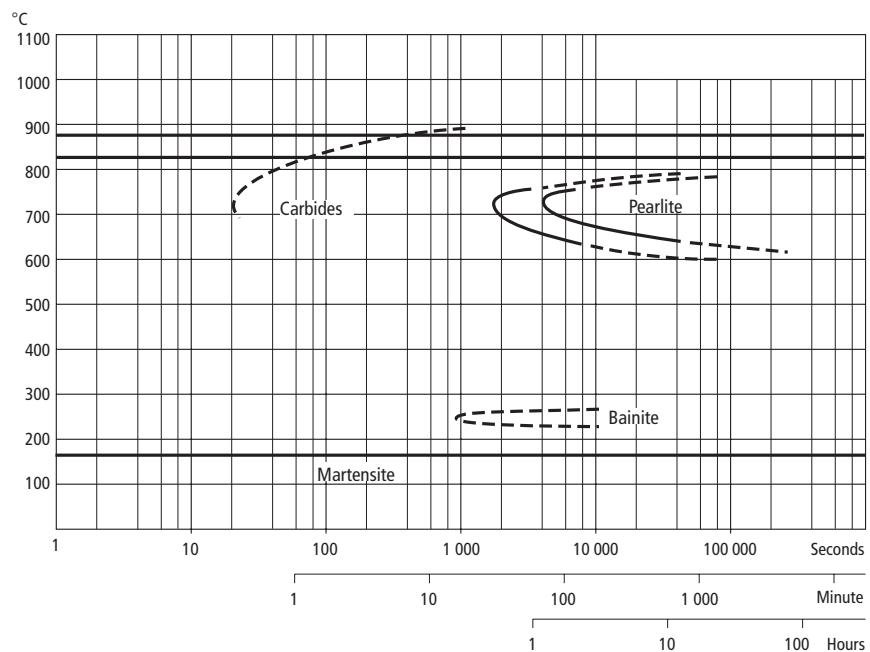

$A_{c1f} = 880^\circ\text{C}$

$A_{c1s} = 830^\circ\text{C}$

Temp. °C.	Time h2	Hardness HV10
800	31,0	498
750	3,1	266
725	1,6	309
700	3,0	304
650	19,6	239
600	23,3	724
300	7,0	813
250	16,3	803
200	23,4	813

## DIMENSIONAL CHANGES

The dimensional changes have been measured after austenitizing and tempering.


*Austenitizing:* 1030°C (1890°F)/30 min, cooling in vacuum furnace at 0,75°C/s (1,35°F/s) between 800°C (1470°F) and 500°C (930°F)

*Tempering:* 2 x 2 h at various temperatures

*Specimen size:* 100 x 100 x 100 mm

*Dimensional changes as function of tempering temperature*

Dimensional changes %

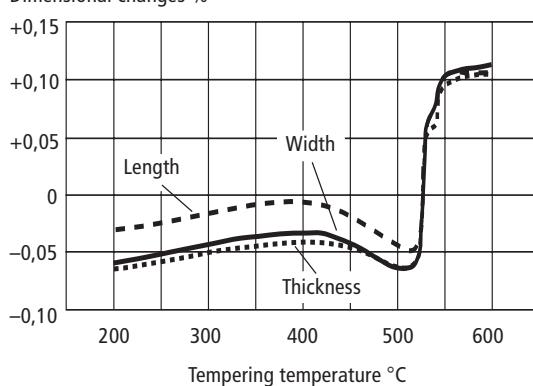


## SUB-ZERO TREATMENT

Pieces requiring maximum dimensional stability in service should be sub-zero treated. Sub-zero treatment reduces the amount of retained austenite and changes the hardness as shown in the diagram below:

*Austenitizing:* 1030°C (1890°F)/30 min

*Tempering:* 2 x 2 h at various temperatures

*Hardness and retained austenite as function of tempering temperature and sub-zero treatment*

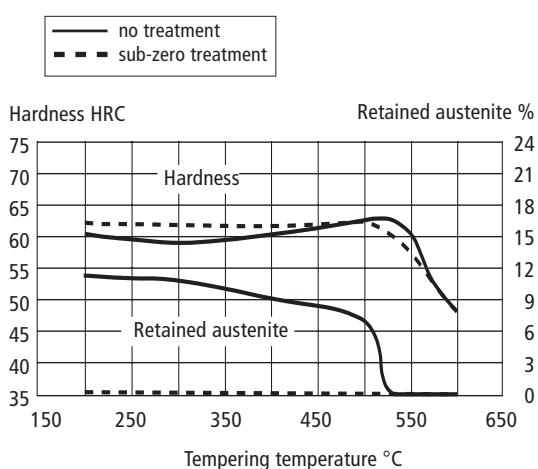

## Surface treatments

Some cold work tool steels are given a surface treatment in order to reduce friction and increase wear resistance. The most commonly used treatments are nitriding and surface coating with wear resistant layers produced via PVD or CVD.

The high hardness and good resistance to chipping together with a good dimensional stability make Sleipner suitable as a substrate steel for various surface coatings.

### NITRIDING AND NITROCARBURIZING

Nitriding and nitrocarburizing result in a hard surface layer which is very resistant to wear and galling. The surface hardness after nitriding is approximately 1100 HV<sub>0,2kg</sub>. The thickness of the layer should be chosen to suit the application in question.

### PVD

Physical vapour deposition, PVD, is a method of applying a wear-resistant coating at temperatures between 200–500°C (390–930°F).

### CVD

Chemical vapour deposition, CVD, is used for applying wear-resistant surface coatings at a temperature of around 1000°C (1830°F). It is recommended that the tools are separately hardened and tempered in a vacuum furnace after surface treatment.



# Machining recommendations

The cutting data below are to be considered as guide values which must be adapted to existing local conditions.

More information can be found in the Uddeholm publication "Cutting data recommendation".

**Condition: Soft annealed to approx. 235 HB.**

## TURNING

Cutting data parameters	Turning with carbide		Turning with high speed steel Fine turning
	Rough turning	Fine turning	
Cutting speed ( $v_c$ ) m/min. f.p.m.	100–150 328–492	150–200 492–656	17–22 56–72
Feed, (f) mm/rev i.p.r.	0,2–0,4 0,008–0,016	0,05–0,2 0,002–0,008	0,05–0,3 0,002–0,01
Depth of cut, ( $a_p$ ) mm inch	2–4 0,08–0,16	0,5–2 0,02–0,08	0,5–3 0,02–0,12
Carbide designation ISO US	K20, P20 C2–C6 Coated carbide	K10, P15 C3, C7 Coated carbide	–

## DRILLING

### High speed steel twist drill

Drill diameter mm	Drill diameter inch	Cutting speed ( $v_c$ )		Feed (f)	
		m/min	f.p.m.	mm/rev	i.p.r.
– 5	–3/16	13–18*	43–59*	0,05–0,10	0,002–0,004
5–10	3/16–3/8	13–18*	43–59*	0,10–0,20	0,004–0,008
10–15	3/8–5/8	13–18*	43–59*	0,20–0,25	0,008–0,010
15–20	5/8–3/4	13–18*	43–59*	0,25–0,30	0,010–0,012

<sup>1)</sup> For coated HSS drill  $v_c$  25–35 m/min. (82–115 f.p.m./min.)

### Carbide drill

Cutting data parameters	Type of drill		
	Indexable insert	Solide carbide	Brazed carbide <sup>1)</sup>
Cutting speed ( $v_c$ ) m/min. f.p.m.	140–160 460–525	80–100 262–328	45–55 148–180
Feed (f) mm/r i.p.r.	0,05–0,15 <sup>2)</sup> 0,002–0,006 <sup>2)</sup>	0,10–0,25 <sup>2)</sup> 0,004–0,01 <sup>2)</sup>	0,15–0,25 <sup>2)</sup> 0,006–0,01 <sup>2)</sup>

<sup>1)</sup> Drill with internal cooling channels and brazed tip.

<sup>2)</sup> Depending on drill diameter.

## MILLING

### Face and square shoulder milling

Cutting data parameters	Milling with carbide	
	Rough milling	Fine milling
Cutting speed ( $v_c$ ) m/min. f.p.m.	110–180 360–590	180–220 590–722
Feed ( $f_z$ ) mm/tooth inch/tooth	0,2–0,4 0,008–0,016	0,1–0,2 0,004–0,008
Depth of cut ( $a_p$ ) mm inch	2–5 0,08–0,2	–2 –0,08
Carbide designation ISO US	K20, P20 C2, C6 Coated carbide	P10–P20 C3–C7 Coated carbide

### End milling

Cutting data parameters	Type of milling		
	Solide carbide	Carbide indexable insert	High speed steel
Cutting speed ( $v_c$ ) m/min. f.p.m.	80–120 262–394	100–140 328–460	13–18 <sup>1)</sup> 43–59 <sup>1)</sup>
Feed ( $f_z$ ) mm/tooth inch/tooth	0,03–0,20 <sup>2)</sup> 0,001–0,008 <sup>2)</sup>	0,08–0,20 <sup>2)</sup> 0,003–0,008 <sup>2)</sup>	0,05–0,35 <sup>2)</sup> 0,002–0,014 <sup>2)</sup>
Carbide designation ISO US	–	P15–P40 C6–C5	–

<sup>1)</sup> For coated HSS end mill  $v_c$  30–35 m/min. (98–115 f.p.m./min.)

<sup>2)</sup> Depending on radial depth of cut and cutter diameter.

## GRINDING

A general grinding wheel recommendation is given below. More information can be found in the Uddeholm publication "Grinding of tool steel".

### Wheel grinding

Type of grinding	Soft annealed condition	Hardened condition
Face grinding straight wheel	A 46 HV	A 46 HV
Face grinding segments	A 24 GV	A 36 GV
Cylindrical grinding	A 46 LV	A 60 KV
Internal grinding	A 46 JV	A 60 JV
Profile grinding	A 100 KV	A 120 JV

## Welding

Good results when welding tool steel can be achieved if proper precautions are taken during the welding operation.

- The joints should be prepared properly.
- Repair welds should be made at elevated temperature. Make the two first layers with the same electrode diameter and/or current.
- Always keep the arc length as short as possible. The electrode should be angled at 90° to the joint sides to minimize undercut. In addition, the electrode should be held at an angle of 75–80° to the direction of forward travel.
- For large repairs, weld the initial layers with a soft filler material (buffering layer)

### FILLER MATERIAL

#### TIG Welding consumables

Filler Material	Hardness after welding
Type AWS ER312	300 HB (for buffering layers)
UTP A67S	55–58 HRC
UTP A696	60–64 HRC
CastoTig 5*	60–64 HRC

\* Should not be used for more than 4 layers because of the increased risk of cracking

#### MMA (SMAW) Welding consumables

Filler Material	Hardness after welding
Type AWS E312	300 HB (for buffering layers)
CASTOLIN 2	54–60 HRC
UTP 67S	55–58 HRC
UTP 69	60–64 HRC
CASTOLIN 6	60–64 HRC

### PREHEATING TEMPERATURE

The temperature of the tool during the entire welding process should be maintained at an even level.

	Soft annealed	Hardened
Hardness	230 HB	60–62 HRC
Preheating temperature	250°C (480°F)	250°C (480°F)
Max. interpass-temperature	400°C (750°F)	400°C (750°F)

### HEAT TREATMENT AFTER WELDING

	Soft annealed	Hardened
Hardness	230 HB	60–62 HRC
Cooling rate	20–40°C/h (40–80°F/h) for the first 2 hours then freely in air	
Heat treatment	Soft anneal Harden Temper	Temper 10–20°C (20–40°F) below the latest tempering temperature

More information on welding of tool steel can be found in the Uddeholm publication "Welding of Tool Steel".

## Flame hardening

Use oxy-acetylene equipment with a capacity of 800–1250 l/h. Oxygen pressure 2,5 bar, acetylene pressure 1,5 bar. Adjust to give neutral flame.

Temperature: 980–1020°C (1795–1870°F). Cool freely in air.

The hardness at the surface will be 58–62 HRC and 41 HRC (400 HB) at a depth of 3–3,5 mm (0,12–0,14").

## Electrical-discharge machining—EDM

If EDM is performed in the hardened and tempered condition, finish with a fine-sparking, i.e. low current, high frequency.

For optimal performance the EDM'd surface should be ground/polished and the tool re-tempered at approx. 25°C (80°F) lower than the original tempering temperature.

When EDM'ing larger sizes or complicated shapes Sleipner should be tempered at high temperature, above 500°C (930°F).

# Relative comparison of Uddeholm cold work tool steel

## MATERIAL PROPERTIES AND RESISTANCE TO FAILURE MECHANISMS

Uddeholm grade	Hardness/ Resistance to plastic deformation	Machinability	Grindability	Dimension stability	Resistance to		Fatigue cracking resistance	
					Abrasive wear	Adhesive wear	Ductility/resistance to chipping	Toughness/gross cracking
ARNE	█	█	█	█	█	█	█	█
CALMAX	█	█	█	█	█	█	█	█
CALDIE	█	█	█	█	█	█	█	█
RIGOR	█	█	█	█	█	█	█	█
SLEIPNER	█	█	█	█	█	█	█	█
SVERKER 21	█	█	█	█	█	█	█	█
SVERKER 3	█	█	█	█	█	█	█	█
VANADIS 4 Extra	█	█	█	█	█	█	█	█
VANADIS 6	█	█	█	█	█	█	█	█
VANADIS 10	█	█	█	█	█	█	█	█
VANADIS 23	█	█	█	█	█	█	█	█

## Further information

Please contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steel.

## UDDEHOLM EUROPE

### AUSTRIA

UDDEHOLM  
Hansallee 321  
D-40549 Düsseldorf  
Telephone: +49 211 535 10  
Telefax: +49 211 535 12 80

### BELGIUM

UDDEHOLM N.V.  
Waterstraat 4  
B-9160 Lokeren  
Telephone: +32 9 349 11 00  
Telefax: +32 9 349 11 11

### CROATIA

BOHLER UDDEHOLM Zagreb  
d.o.o za trgovinu  
Zitnjak b.b  
10000 Zagreb  
Telephone: +385 1 2459 301  
Telefax: +385 1 2406 790

### CZECHIA

BOHLER UDDEHOLM CZ s.r.o.  
Division Uddeholm  
U silnice 949  
161 00 Praha 6 Ruzyně  
Czech Republic  
Telephone: +420 233 029 850,8  
Telefax: +420 233 029 859

### DENMARK

UDDEHOLM A/S  
Kokmose 8, Bramdrupdam  
DK-6000 Kolding  
Telephone: +45 75 51 70 66  
Telefax: +45 75 51 70 44

### ESTONIA

UDDEHOLM TOOLING AB  
Siliikatsiidi 7  
EE-0012 Tallinn  
Telephone: +372 655 9180  
Telefax: +372 655 9181

### FINLAND

OY UDDEHOLM AB  
Ritakuja 1, PL 57,  
FIN-01741 VANTAA  
Telephone: +358 9 290 490  
Telefax: +358 9 2904 9249

### FRANCE

UDDEHOLM S.A.  
12 Rue Mercier, Z.I. de Mitry-Compans  
F-77297 Mitry Mory Cedex  
Telephone: +33 (0)1 60 93 80 10  
Telefax: +33 (0)1 60 93 80 01

#### Branch office

UDDEHOLM S.A.  
77bis, rue de Vesoul  
La Nef aux Métiers  
F-25000 Besançon  
Telephone: +33 381 53 12 19  
Telefax: +33 381 53 13 20

### GERMANY

UDDEHOLM  
Hansallee 321  
D-40549 Düsseldorf  
Telephone: +49 211 535 10  
Telefax: +49 211 535 12 80

#### Branch offices

UDDEHOLM  
Falkenstraße 21  
D-65812 Bad Soden/T.S.  
Telephone: +49 6196 659 60  
Telefax: +49 6196 659 625

### UDDEHOLM

Albstraße 10  
D-73765 Neuhausen  
Telephone: +49 715 898 65-0  
Telefax: +49 715 898 65-25

### GREAT BRITAIN, IRELAND

UDDEHOLM UK LIMITED  
European Business Park  
Taylors Lane, Oldbury  
West Midlands B69 2BN  
Telephone: +44 121 552 55 11  
Telefax: +44 121 544 29 11  
Dublin Telephone: +353 1 45 14 01

## GREECE

UDDEHOLM STEEL TRADING  
COMPANY  
20, Athinon Street  
G-Piraeus 18540  
Telephone: +30 2 10 41 72 109/41 29 820  
Telefax: +30 2 10 41 72 767

### SKLERO S.A.

Steel Trading Comp. and  
Hardening Shop  
Frixou 11/Nikif. Ouranou  
G-54627 Thessaloniki  
Telephone: +30 31 51 46 77  
Telefax +30 31 54 12 50

## HUNGARY

UDDEHOLM TOOLING/BOK  
Dunaharaszti, Jedlik Ányos út 25  
H-2331 Dunaharaszti 1.Pf. 110  
Telephone/Telefax: +36 24 492 690

## ITALY

UDDEHOLM Italia S.p.A.  
Via Palizzi, 90  
I-20157 Milano  
Telephone: +39 02 35 79 41  
Telefax: +39 02 390 024 82

## LATVIA

UDDEHOLM TOOLING AB  
Deglava street 50  
LV-1035 Riga  
Telephone: +371 7 701 983, -981, -982  
Telefax: +371 7 701 984

## LITHUANIA

UDDEHOLM TOOLING AB  
BE PLIENAS IR METALAI  
T. Masiulio 18b  
LT-3014 Kaunas  
Telephone: +370 37 370613, -669  
Telefax: +370 37 370300

## THE NETHERLANDS

UDDEHOLM B.V.  
Isolatorweg 30  
NL-1014 AS Amsterdam  
Telephone: +31 20 581 71 11  
Telefax: +31 20 684 86 13

## NORWAY

UDDEHOLM A/S  
Jernkroken 18  
Postboks 85, Kalbakken  
N-0902 Oslo  
Telephone: +47 22 91 80 00  
Telefax: +47 22 91 80 01

## POLAND

INTER STAL CENTRUM  
Sp. z. o.o./Co. Ltd.  
ul. Kolejowa 291, Dziekanów Polski  
PL-05-092 Lomianki  
Telephone: +48 22 429 2260  
Telefax: +48 22 429 2266

## PORTUGAL

F RAMADA Aços e Industrias S.A.  
P.O. Box 10  
P-3881 Ovar Codex  
Telephone: +351 56 58 61 11  
Telefax: +351 56 58 60 24

## ROMANIA

BÖHLER Romania SRL  
Uddeholm Branch  
Str. Atomistilor Nr 14A  
077125 Magurele Jud Ilfov  
Telephone: +40 214 575007  
Telefax: +40 214 574212

## RUSSIA

UDDEHOLM TOOLING CIS  
25 A Bolshoy pr PS  
197198 St. Petersburg  
Telephone: +7 812 233 9683  
Telefax: +7 812 232 4679

## SLOVAKIA

UDDEHOLM Slovakia  
Nástrojové oceľe, s.r.o.  
KRÁCINY 2  
036 01 Martin  
Telephone: +421 842 4 300 823  
Telefax: +421 842 4 224 028

## SLOVENIA

UDDEHOLM Italia S.p.A.  
Via Palizzi, 90  
I-20157 Milano  
Telephone: +39 02 35 79 41  
Telefax: +39 02 390 024 82

## SPAIN

UDDEHOLM  
Guifré 690-692  
E-08918 Badalona, Barcelona  
Telephone: +34 93 460 1227  
Telefax: +34 93 460 0558

#### Branch office

UDDEHOLM  
Barrio San Martin de Arteaga, 132  
Pol.Ind. Torrelarragoiti  
E-48170 Zamudio  
(Bizkaia)  
Telephone: +34 94 452 13 03  
Telefax: +34 94 452 13 58

## SWEDEN

UDDEHOLM TOOLING  
SVENSKA AB  
Aminogatan 25  
SE-431 53 Mölndal  
Telephone: +46 31 67 98 50  
Telefax: +46 31 27 02 94

## SWITZERLAND

HERTSCH & CIE AG  
General Wille Strasse 19  
CH-8027 Zürich  
Telephone: +41 1 208 16 66  
Telefax: +41 1 201 46 15

## UDDEHOLM NORTH AMERICA

### USA

UDDEHOLM  
4902 Tollview Drive  
Rolling Meadows IL 60008  
Telephone: +1 847 577 22 20  
Telefax: +1 847 577 80 28

UDDEHOLM  
548 Clayton Ct.,  
Wood Dale IL 60191  
Telephone: +1 630 350 10 00  
Telefax: +1 630 350 08 80

UDDEHOLM  
9331 Santa Fe Springs Road  
Santa Fe Springs, CA 90670  
Telephone: +1 562 946 65 03  
Telefax: +1 562 946 77 21

UDDEHOLM  
220 Cherry Street  
Shrewsbury, MA 01545  
Telephone: +1 508 845 1066  
Telefax: +1 508 845 3471

### CANADA

UDDEHOLM LIMITED  
2595 Meadowvale Blvd.  
Mississauga, Ontario LSN 7Y3  
Telephone: +1 905 812 9440  
Telefax: +1 905 812 8659

## MEXICO

ACEROS BOHLER UDDEHOLM,  
S.A. de C.V.  
Calle 8 No 2, Letra "C"  
Fraccionamiento Industrial Alce Blanco  
C.P. 52787 Naucalpan de Juarez  
Estado de Mexico  
Telephone: +52 55 9172 0242  
Telefax: +52 55 5576 6837

UDDEHOLM  
Lerdo de Tejada No.542  
Colonia Las Villas  
66420 San Nicolas de Los Garza, N.L.  
Telephone: +52 8-352 5239  
Telefax: +52 8-352 5356

## UDDEHOLM SOUTH AMERICA

### ARGENTINA

UDDEHOLM S.A.  
Mozart 40  
1619-Centro Industrial Garin  
Garin-Prov. Buenos Aires  
Telephone: +54 332 744 4440  
Telefax: +54 332 745 3222

### BRAZIL

UDDEHOLM ACOS ESPECIAIS Ltda.  
Estrada Yae Massumoto, 353  
CEP 09842-160  
Sao Bernardo do Campo - SP Brazil  
Telephone: +55 11 4393 4560, -4554  
Telefax: +55 11 4393 4561

## UDDEHOLM SOUTH AFRICA

UDDEHOLM Africa (Pey) Ltd.  
P.O. Box 539  
ZA-1600 Isando/Johannesburg  
Telephone: +27 11-974 2781  
Telefax: +27 11-392 2486

## UDDEHOLM AUSTRALIA

BOHLER-UDDEHOLM Australia  
129-135 McCredie Road  
Guildford NSW 2161  
Private Bag 14  
Telephone: +61 2 9681 3100  
Telefax: +61 2 9632 6161

#### Branch offices

Sydney, Melbourne, Adelaide,  
Brisbane, Perth, Newcastle,  
Launceston, Albury, Townsville

## ASSAB

### ASSAB INTERNATIONAL

Skytteholmsvägen 2  
P O Box 42  
SE-171 11 Solna  
Sweden  
Telephone: +46 8 564 616 70  
Telefax: +46 8 25 02 37

#### Subsidiaries

India, Iran, Turkey, United Arab  
Emirates

*Distributors in*  
Africa, Latin America, Middle East

### ASSAB PACIFIC

ASSAB Pacific Pte. Ltd  
171, Chin Swee Road  
No. 07-02, San Centre  
Singapore 169877  
Telephone: +65 534 56 00  
Telefax: +65 534 06 55

#### Subsidiaries

China, Hong Kong, Indonesia, Japan,  
Korea, Malaysia, Philippine Islands,  
Singapore, Taiwan, Thailand

When the first idea pops into your head, throughout the development process to the release of the new product, we'll be your partner. As the world's leading supplier of tooling materials and related services, we can be trusted. Meet us under the Uddeholm and ASSAB brands, wherever in the world you have your business.

